

MECHANICAL PROPERTIES OF REACTIVE POWDER CONCRETE BY USING FLY ASH

A.D.Agharde¹, Dr.S.A.Bhalchandra²

¹Applied Mechanics Department, Government Engineering College, Aurangabad, Maharashtra (India)

²Associate Prof., Applied Mechanics Dept., Govt. Engg. College, Aurangabad, Maharashtra (India)

ABSTRACT

Reactive Powder Concrete is a developing composite material that will allow the concrete industry to optimize material use, Generate economic benefits, and build structures that are strong, durable, and sensitive to environment. RPC is a new ultra-high performance concrete with wide range of capabilities. RPC was developed in the 1990s by Bouygues' laboratory in France. RPC represents a new class of Portland cement-based material with compressive strengths of 200 MPa range. By introducing fine steel fibers RPC can achieve flexural strength up to 50 MPa. It has no coarse aggregates and contains small steel fibres that provide additional strength. RPC include Portland cement, silica flour, fine sand, superplasticizer, water and steel fibres. The main object of this study is to check the effect of replacing silica fume by fly ash and percentage variation of steel fiber on reactive powder concrete, to achieve economy without any significant change in properties of RPC. The silica fume is replaced by the fly ash by its weight variation of 0% to 50% with interval of 10 %. It was found that replacement of fly ash upto 40% by silica fume is economical to achieve high compressive strength upto 90 MPa under normal curing. Percentage of fiber content vary from 0 % to 1 % with interval of 0.25%, It was found that addition of 0.75 percentage of fibres content gives better flexural and tensile strength.

Keywords- Fly Ash, Precipitated Silica, Reactive Powder Concrete, RPC, Steel Fibers, Silica Fume

1. INTRODUCTION

Concrete, one of the most widely used construction materials, has been subject to major research and development over the past century. The high performance concrete (HPC) is also a new trend concrete material that enhances high strength upto 120 MPa, but Richard and Cheyrezy show that Reactive powder concrete (RPC) in which strength is obtained in excess of 200 MPa and flexural strength 30-60 MPa [1]. Comparison of the physical, mechanical, and durability properties of RPC and HPC (High Performance concrete) shows that RPC possesses better strength.

Reactive Powder concrete contains very fine materials such as precipitated silica, crushed sand and silica fume. The basic composition for the production of RPC has been explained by the Richard and Cheyrezy [1]. A very dense matrix is achieved by optimizing the granular packing of these powders [2]. Due to inverse effect of high cement content on the early age shrinkage behavior and decreased hardened performance by micro-cracking, supplementary cementations materials such as fly ash, blast furnace slag, and silica fume are commonly used in cement and concrete industry [3]. It is possible to modify some fresh and hardened properties of composite by utilizing these materials. In this study, it has been checked that effect of fly ash as a replacement of silica fume on the parameters of reactive powder concrete such as compressive, tensile and flexural strength.

2. MATERIALS

The material used for this experiment work is cement, fly ash, silica fume, quartz flour, fine silica sand, high range water reducer, steel fibres, and water.

2.1. Cement

Cement used for present work are 53 grade ordinary Portland cement. Its properties tested as per IS 269-1989[4] are shown in table 1.

TABLE 1: Properties of Cement

Fineness of cement	Specific gravity	Standard constancy	Setting time		28 days compressive strength
			Initial	Final	
3.12%	3.15	30%	160 minutes	250 minutes	66 N/mm ²

2.2. Fine sand

Artificial sand used is angular in shape. Its properties tested as per I.S.383-1970[5] are shown in table 2.

TABLE 2: Properties of Fine Sand

Particle size	Specific gravity	Silt /dust content	Surface moisture	Water absorption
150-400 micron	2.96	Nil	0.42%	2.30%

2.3. Precipitated silica and Silica flour

Properties of precipitated silica and silica flour are as shown in table 3.

TABLE 3: Properties Of Precipitated Silica & Silica Flour

Material→	Precipitated silica	Silica flour
Properties↓		
Particle size	5 to 100nm	300 micron
Colour	White	White
Silica content	99.24 %	91 %
Specific gravity	2.7	2.2

2.4. Fly ash

Fly ash used for this work is pozocrete 60. Its properties are as shown in table 4

TABLE 4: Properties Of Fly Ash

Appearance	Specific surface area	Specific gravity	Silica content
White	5-100 m ² /g	2.2	65 %

2.5. Super plasticizer

Acrylic polymer based-Dynamon SX superplasticizer used in this work. Its properties are as shown in table 5.

TABLE 5: Properties of Superplasticizer

Consistency	Appearance	Density	Alkali content	Chloride content	Air entrainment	Nitrate content
Liquid	Amber	1.07 @20°C	<2.5	<0.1	Nil	Nil

3. EXPERIMENTAL ANALYSIS

RPC composition used in this study, we referred Richard and Cheyrezy [6] mix proportion from their research. Using this reference, the trial mix were taken by adjusting percentages of silica fume. According to trial mixes appropriate mixes were taken for actual mixing. The aim was to find out the highest compressive strength at optimum percentage of fly ash and silica fume. The quantity of ingredient materials and mix proportion of RPC is given in following table.

TABLE 6: Composition Of RPC

Composition	Silica/Crushed sand	Portland cement	Precipitated silica	Silica fume	super plasticizer	Total water
Content (kg/m ³)	1031	937	9.4	225	18	Adjusted

Concrete of mix proportion as shown in (table 6) was prepared and then silica fume content is replaced by fly ash. Fly ash content varies from 10 to 50%. For compressive strength, test specimens (100mm x 100mm x 100 mm) were prepared with the percentage of fly ash which replace silica fume as a 100% SF, 10%, 20%, 30%, 40%, 50%. The mixes are denoted by M_{F10}, M_{F20}, M_{F30}, M_{F40}, and M_{F50} and for flexural strength; specimens were prepared with percentage of steel fiber such as 0.25 to 1 % of volume of concrete used for testing properties of RPC. The mixes are denoted by M₁, M₂, M₃, M₄, and M₅. The specimens were kept in the moulds for 24 hours at room temperature of 20°C. After demolding, the specimens were cured by standard normal curing procedure.

4. TEST ON HARDENED CONCRETE: Confirming to IS 516-1959[7]

4.1 Compressive Strength Test

A cube compression test performed on standard cubes of reactive powder concrete of size 100mmX100mmX100mm after 7 days and 28 days of immersed in water. The compressive strength of specimens was calculated by the following formula

$$\text{Equation 1: } F_{cu} = P_c / A$$

Where

P_c = Failure load in compression, kN

A = Loaded area of cube, mm^2

4.2 Flexural Strength Test

Standard beams of size 100 x 100 x 500mm were supported symmetrically over a span of 400mm and subjected two points loading till failure of the specimen. The deflection at the center of the beam is measured with sensitive dial gauge on UTM. The two broken pieces (prisms) of flexure test were further used for equivalent cube compressive strength. The flexural strength was determined by the formula.

$$\text{Equation 2: } f_{cr} = \frac{P_f L}{bd^2}$$

Where

P_f = Central point through two point loading system, kN

L = Span of beam, mm

b = Width of beam, mm

d = Depth of beam, mm

5. RESULTS AND DISCUSSION

5.1 Compressive strength

The results of compressive strength are obtained using equation (1). Test results of RPC after standard water curing (7 and 28 days) are shown in table 7. The compressive strength of 100% silica fume mixture is nearly about 80 MPa and Percentage of fly ash which replaces silica fume upto 20% shows slight increase in compressive strength and at 30% fly ash gives the strength near about 87 Mpa after 28-days standard curing. After that as fly ash content increases compressive strength reduces as shown in Fig no.1.

TABLE 8: Compressive Strength

Mixes→		100 % SF	M_{F10}	M_{F20}	M_{F30}	M_{F40}	M_{F50}
Strengths↓	Curing Days						
Compressive Strength(MPa)	7	70.75	65.40	68.82	75.12	73.73	68.13
	28	80	77.34	85.67	86	84.3	78.17
% Variation in Compressive Strength(MPa)	7	0.00	7.56	2.72	6.17	1.47	3.70
	28	0.00	3.33	7.08	7.5	4.3	2.22

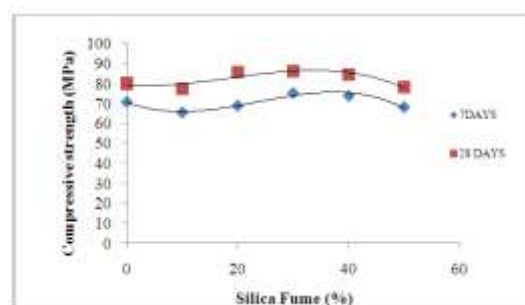


Figure 1: effect of silica fume on compressive strength

5.2 Flexural Strength

The results of Flexural strength are obtained using equation (2) For better flexural strength at 7 and 28 days, we use the proportion of fly ash silica fume is 30:70. From the test result in table no.8, it can be seen that, As the volume fraction increases from 0.25 to 0.75, flexural strength increases upto 22 Mpa. It is observed that for 1% fibers, flexural strength decreases as shown in Fig 2.

TABLE 8: Flexural Strength

Mixes→		M ₀	M ₁	M ₂	M ₃	M ₄
Strengths↓	Curing Days					
Flexural Strength(MPa)	7	9	10.5	13.1	16.3	14.23
	28	11.23	14.7	16.2	22	18.34
% Variation in Flexural Strength(MPa)	7	0.00	16.66	45.55	81.11	58.11
	28	0.00	30.89	44.25	95.90	63.31

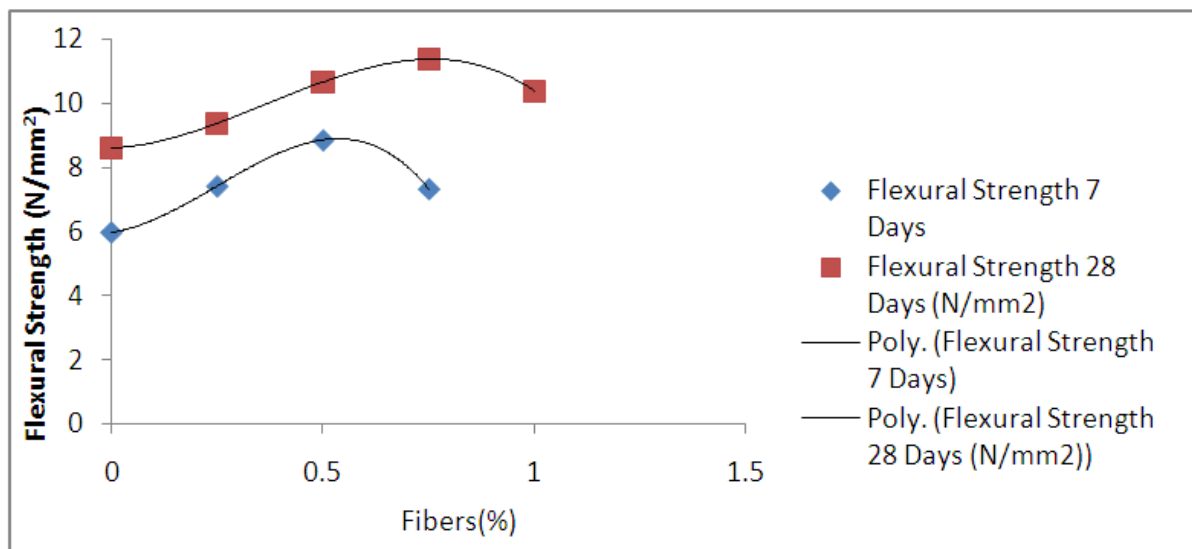


Figure 2: effect of addition of steel fibers on flexural strength

6. CONCLUSION

The main objective of this study is to Study the effect of replacement of fly ash over silica fume and variation of steel fiber in RPC. This study shows the optimum percentage of fly ash to replace some amount of silica fume. Based on the results obtained from the tests conducted on this study some general conclusions may be drawn.

1. Replacement of fly ash over silica fume is economically. The Compressive strength is increase upto 86 Mpa by increasing fly ash at 30%. After that strength reduces.

2. The composite mineral admixtures is attributed to the partial packing, filling effect, pozzolanic effect which improve strength, very compacted RPC matrix with low porosity.
3. The incorporation of metallic fibers improves the flexural strength of RPC; Flexural strength increases up to 16 Mpa by increasing fly ash at 30%. After that strength reduces.

REFERENCES

- [1]. P. Richard and M.H Cheyrezy (1994) "*Reactive powder concretes with high ductility and 200 – 800 MPa compressive strength*", *ACI SP 144*:507–5.
- [2]. Olivier Bonneau, b, c, Christian Vernet, Micheline Moranville, c, Pierre-Claude Atina. "*Characterization of the granular packing and percolation threshold of reactive powder concrete*." *Cement and Concrete Research* 30 (2000) 1861-1867.
- [3]. Zhang Yunsheng *, Sun Wei, Liu Sifeng, Jiao Chujie, Lai Jianzhong (2008), "*Preparation of C200 green reactive powder concrete and its static–dynamic behaviors*" *Cement & Concrete Composites* 30, 831–838.
- [4]. I.S.269-1989, "*Ordinary Portland Cement, 33 Grade Specification*, (Fourth Edition), Bureau of Indian Standard, New Delhi,
- [5]. I.S.383-1970, "*Indian Standard Specification for coarse and fine aggregates from natural sources for concrete*, (Second Revision)", Bureau of Indian Standard, New Delhi, 1970.
- [6]. P. Richard and M. H. Cheyrezy, (1994) "*Reactive powder concretes with high ductility and 200-800 MPa compressive strength*." *Concrete Technology: Past, Present, and Future - V. Mohan Malhotra Symposium, San Francisco, CA*, 507-518.
- [7]. I.S.516-1959, "*Method of Tests for Strength of Concrete*," Bureau of Indian Standard, New Delhi.